

Order from disorder in the double-exchange model

Nic Shannon

Max-Planck-Institut für Physik komplexer Systeme, Nöthnitzer Str. 38, 01187 Dresden, Germany.

Andrey V. Chubukov

Department of Physics, University of Wisconsin-Madison, 1150 Univ. Av., Madison WI 53706, USA.

(February 1, 2008)

The magnetic excitations of the double exchange (DE) model are usually discussed in terms of an equivalent ferromagnetic Heisenberg model. However this equivalence is valid *only* at a quasi-classical level — we show that both quantum and thermal corrections to the magnetic properties of DE model differ from *any* effective Heisenberg model because its spin excitations interact only indirectly, through the exchange of charge fluctuations. We also find that the competition between ferromagnetic double exchange and an antiferromagnetic superexchange provides a new example of an “order from disorder” phenomenon — an intermediate spin configuration (either a canted or a spiral state) is selected by quantum and/or thermal fluctuations.

Many magnetic systems of current experimental interest, for example the colossal magnetoresistance (CMR) Manganites [1,2] and Pyrochlores [3], consist of itinerant electrons interacting with an array of localized magnetic moments with spin S . The simplest models of these systems comprise a single tight binding band of electrons interacting with localized core spins by a ferromagnetic (Hund’s rule) exchange interaction $J_H \gg t$

$$\mathcal{H}_1 = -t \sum_{\langle ij \rangle \alpha} c_{i\alpha}^\dagger c_{j\alpha} - J_H \sum_{i\alpha\beta} \vec{S}_i \cdot c_{i\alpha}^\dagger \vec{\sigma}_{\alpha\beta} c_{i\beta} \quad (1)$$

where the sum $\langle ij \rangle$ is restricted to neighboring sites. At a classical level, the ground state of this model in $D > 1$ must be ferromagnetic, since the Hund’s rule requires the spin of itinerant electrons to be locally aligned with the core spins, and the kinetic energy of electrons is in turn minimized by making all the electron spins parallel. This effect is usually called “double exchange”, and in this context the model of Eq. (1) is referred to as the double exchange ferromagnet (DEFM).

At a quasi-classical level the spin dynamics in a DEFM can be described by an effective nearest-neighbor Heisenberg model $-J_1 \sum_{\langle ij \rangle} \vec{S}_i \cdot \vec{S}_j$ with ferromagnetic exchange integral $J_1 = \bar{t}/4S^2$, where $\bar{t}$ is the expectation value of the kinetic energy per bond in the lattice [4–8,12]. In addition, core spins also interact via a direct superexchange

$$\mathcal{H}_2 = J_2 \sum_{\langle ij \rangle} \vec{S}_i \cdot \vec{S}_j \quad (2)$$

In CMR materials, J_2 is believed to be positive (antiferromagnetic), and so competes with the DE mechanism.

A natural question to ask is how a system described by $\mathcal{H} = \mathcal{H}_1 + \mathcal{H}_2$ evolves towards an antiferromagnet with increasing J_2 ? As observed by de Gennes [4], for classical spins ($S \rightarrow \infty$), the FM becomes unstable at $J_1/J_2 = 1$. At larger J_2 , the competition between J_2 and the kinetic energy gives rise to an intermediate phase where

the neighboring lattice spins are misaligned by an angle θ , where $\cos \theta/2 = J_1/J_2$ (in this regime, the DE model is no longer equivalent to Heisenberg model). However, θ alone does not specify a particular intermediate configuration — there exist an infinite set of classically degenerate states with the same θ . The two ends of this set are the two-sublattice canted phase and the spiral phase [4].

We performed a spin-wave analysis for the canted phase of the DEFM and found $\omega_{sw}(q) \equiv 0$ for all q . This result reflects the local symmetry linking all the different classical groundstates — we can take any (classical) spin on the A sublattice of the canted phase and rotate it about the direction of magnetization of the B sublattice without changing the angle θ . Since it costs no energy to make such an excitation, the system cannot distinguish between different states, and is magnetically disordered even at $T = 0$ [4]. This argument, however, does not hold at finite S , and we anticipate that quantum and/or thermal fluctuations will enable the system to choose its true groundstate. Such “order from disorder” effects have been widely discussed in the context of magnetic insulators, e. g. for Kagomé antiferromagnets [13] — but not in the context of the metallic DEFM.

The most direct route to an answer to what kind of order is preferred in the DE model is to determine the first instability of the DEFM, by looking for the wave vector Q^* at which the spin-wave dispersion becomes unstable. The quasi-classical arguments leading to an effective Heisenberg model *cannot* answer this question since they predict a FM spinwave spectrum of the form $\omega_{sw}(q) = 2zS(J_1 - J_2)(1 - \gamma_q)$, where z is the lattice coordination number, and $\gamma_q = (1/z) \sum_{\delta} e^{i\vec{k}\cdot\vec{\delta}}$ where $\{\vec{\delta}\}$ runs over nearest neighbors. Thus $\omega_{sw}(q)$ vanishes identically for $J_2 = J_1$, and no special wave vector is singled out. In order to find the true groundstate for $J_2 > J_1$, we then must go beyond the usual mapping of the DEFM onto an effective Heisenberg model.

In this paper we argue that the equivalence between DEFM and the nearest-neighbor Heisenberg ferromagnet holds only for $S \rightarrow \infty$, while fluctuation corrections in the DEFM are governed by fermions and are different from those in the Heisenberg model. We show analytically that for both small densities of electrons ($x \ll 1$) and small densities of holes ($1 - x \ll 1$), the first instability of the DEFM is against a two-sublattice canted structure with $Q^* = (\pi, \pi, \pi)$. At intermediate densities ($0.3 \lesssim x \lesssim 0.9$ in $3D$), the first instability is against a spiral spin configuration with $Q^* \approx (0, 0, 0)$. Similar results hold for the $2D$ case. We also show that thermal corrections to $\omega_{sw}(q)$ compete with the quantum corrections, and the trade-off between these two effects gives rise to re-entrant transition between canted and spiral phases with increasing T .

The nonequivalence between DEFM and the Heisenberg ferromagnet has been earlier detected in numerical studies [9–11]. Analytically, this has been demonstrated at $T = 0$ by Golosov [12]. Our $T = 0$ results agree with his, but we present more physical understanding. Our calculation scheme and results at $T \neq 0$ are entirely new.

We now turn to the calculations. Given that the the Hund's rule coupling J_H is the largest energy scale in the problem it is desirable to diagonalize this term first and project out all electrons not locally aligned with the core spins. We should also define spin-wave excitations such that they are the true Goldstone modes of the order parameter, i. e. transverse fluctuations of the composite spin $\vec{S}_i = \vec{S}_i + \frac{1}{2} \sum_{\alpha\beta} c_{i\alpha}^\dagger \vec{\sigma}_{\alpha\beta} c_{i\beta}$. We can accomplish both of these goals by the following procedure: (i) introducing new Fermi operators f_i and p_i which create electronic “up” and “down” states aligned with the quantization axis of the composite spin, and (ii) generalizing the Holstein–Primakoff transformation to the case where the length of the spin is itself an operator, introducing a corresponding bosonic operator $\tilde{a}$. We work in the large S limit usual for spin-wave theories. Full details of the transformation will be given elsewhere [14]; here we simply state that the transformation and its inverse are unitary, and satisfy all required (anti-)commutation relations e. g. $\{f, f^\dagger\} = \{p, p^\dagger\} = [\tilde{a}, \tilde{a}^\dagger] = 1$, $[f, \tilde{a}] = \{f, p\} = 0$ etc. We have also checked that our expansion procedure reproduces all features of an exact solution of the DE model on two sites [15].

Although the full analysis of the order from disorder phenomenon required us to derive the transformation to order $1/S^2$, to capture the essential physics it is sufficient to know the inverse transformation to order $1/S$. To this order we have

$$a = \tilde{a} \left(1 + \frac{p^\dagger p - f^\dagger f}{4S} \right) - \frac{f^\dagger p}{\sqrt{2S}} + \mathcal{O}(1/S^{3/2})$$

$$c_\uparrow = f \left(1 - \frac{\tilde{a}^\dagger \tilde{a} + p^\dagger p}{4S} \right) - \frac{p \tilde{a}^\dagger}{\sqrt{2S}} + \mathcal{O}(1/S^{3/2})$$

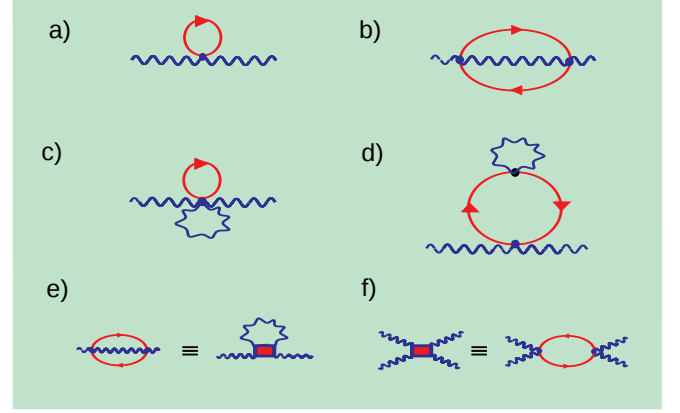


FIG. 1. a)–d) Diagrams contributing to spin-wave self energy in Ferromagnet to order $\mathcal{O}(1/S^2)$. Only diagrams a) and b) are physically relevant. e)–f) The representation of the diagram b) via an effective four-boson interaction mediated by the charge susceptibility (particle-hole polarization bubble).

$$c_\downarrow = p \left(1 - \frac{\tilde{a}^\dagger \tilde{a} + f f^\dagger}{4S} \right) + \frac{f \tilde{a}}{\sqrt{2S}} + \mathcal{O}(1/S^{3/2}) \quad (3)$$

where a is the Holstein–Primakoff boson associated with the core spin. Substituting this transformation into (1), we find that the Hund rule term in (1) does not contain any spin operators and reduces to

$$\mathcal{H}_1 = -\frac{J_H S}{2} \left[f^\dagger f - p^\dagger p \left(1 + \frac{1}{S} \right) + \frac{f^\dagger f p^\dagger p}{S} \right] \quad (4)$$

Clearly, p operators describe high-energy excitations and can be safely dropped. Simultaneously, the hopping term in (1) transforms into the Hamiltonian which describes a single band of spinless fermions interacting with (initially dispersionless) Holstein–Primakoff bosons:

$$\mathcal{H}_t = \sum_{\vec{k}} (\epsilon_k - \mu) f_k^\dagger f_k + \frac{1}{N} \sum_{\vec{k}_1 \dots \vec{k}_4} V_{24}^{13} f_1^\dagger f_2^\dagger \tilde{a}_3^\dagger \tilde{a}_4 + \dots \quad (5)$$

where $\epsilon_k = -J_H S/2 - zt\gamma_k$, and

$$V_{24}^{13} = \frac{zt}{4(S + \frac{1}{2})} \left[(\gamma_1 + \gamma_2) \left(1 + \frac{1}{8S} \right) - (\gamma_{1+3} + \gamma_{2+4}) \right] \quad (6)$$

The perturbation theory for the bosonic propagator $D(q, \Omega)$ is straightforward. We have $D^{-1}(q, \Omega) = \Omega - \Sigma(q, \Omega)$. The self-energy physically comes from the fact that the oscillations of the core spins destroy perfect alignment of electron spins, and this increases electron kinetic energy. To $\mathcal{O}(1/S)$, $\Sigma(q, \Omega)$ comes from a single loop of fermions Fig. 1a and evaluates to

$$\Sigma^{(1a)}(q) = 2zJ_1 S [1 - \gamma_q] ; J_1 = \frac{t}{4S^2} \frac{1}{N} \sum_{\vec{k}} n_k \gamma_k. \quad (7)$$

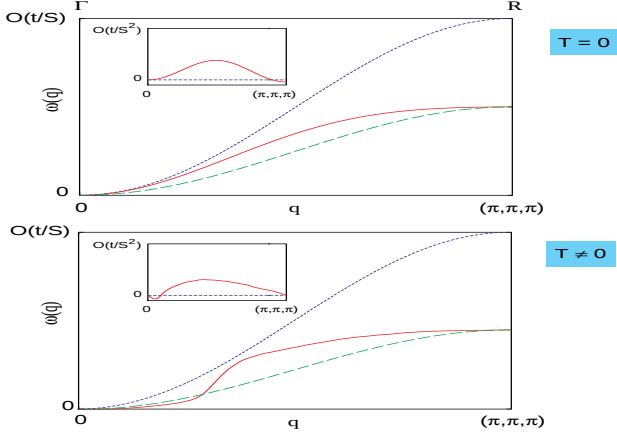


FIG. 2. Schematic corrections to the spin-wave dispersion in the (1,1,1) direction at zero and finite temperatures and small electron density x . Dotted lines show zero temperature classical ($\mathcal{O}(1/S)$) dispersion; dashed lines show renormalized classical dispersion at $\mathcal{O}(1/S^2)$; solid lines show spectrum including all quantum/thermal effects at $\mathcal{O}(1/S^2)$. Insets show residual dispersion at instability against canted ($T = 0$) and spiral ($T \neq 0$) phases

so at this level we indeed reproduce the spin-wave spectrum of a nearest-neighbor Heisenberg FM.

The calculation of the spin-wave dispersion at higher order requires some care. There are four self energy contributions at $\mathcal{O}(1/S^2)$, one from each of the diagrams in Fig. 1a–d. At finite temperature these include a contribution from a six-fold term in $\mathcal{H}_t$, omitted in Eqn. 5. However there is considerable cancellation between terms, and all important physical effects come from the diagram Fig. 1b, which can be thought of as an effective four-boson interaction mediated by Fermions (Fig. 1e–f). Assembling all contributions to the self-energy, splitting it into quantum and thermal pieces, and neglecting the frequency dependence of the self-energy (which is $\mathcal{O}(1/S^3)$), we obtain a renormalized spin-wave dispersion $\Omega(q) = 2zJ_1S(1 - \gamma_q) + \Sigma_{T=0}^{(2)}(q) + \Sigma_T^{(2)}(q)$ where

$$\Sigma_{T=0}^{(2)}(q) = -\frac{zt}{4S^2} \frac{1}{N^2} \sum_{p,l} n_F(p)(1 - n_F(l)) \times \left[(1 - \gamma_q)\gamma_p \frac{\gamma_p + \gamma_l}{\gamma_p - \gamma_l} - \frac{\gamma_p^2 - \gamma_{q+p}^2}{\gamma_p - \gamma_l} \right] \quad (8)$$

and

$$\Sigma_T^{(2)}(q) = -\frac{zt}{4S^2} \frac{1}{N^2} \sum_{p,l} n_B(l) \frac{n_F(p + \frac{m}{2}) - n_F(p - \frac{m}{2})}{\gamma_{p+m/2} - \gamma_{p-m/2}} \times (\gamma_{p-m/2} - \gamma_{p+q-m/2})(\gamma_{p+m/2} - \gamma_{p+q-m/2}). \quad (9)$$

Here $\vec{m} = \vec{q} - \vec{l}$, and $n_B(q) = n_B(\Omega(q))$ and $n_F(k) = n_F(\epsilon_k)$ are Bose and Fermi distribution functions, respec-

tively. The latter can be approximated by step functions as we will be interested in $T < J_1S \ll t$.

We now analyze the form of $\Sigma^{(2)}(q)$, beginning with the case $T = 0$. The first term in (8) simply renormalizes the classical Heisenberg-like spinwave dispersion, while the second has a dependence on q which is quite different from that in the nearest-neighbor Heisenberg model. This term is either positive or negative throughout the Brillouin zone, depending on the electronic density, and is symmetric under $\vec{q} \rightarrow \vec{\pi} - \vec{q}$ where $\vec{\pi} = (\pi, \pi, \pi)$. Along the zone diagonal, it reduces to $\frac{zt}{4S^2} I(x) [1 - \cos(2q)]$ where $I(x) = (1/N^2) \sum_{pl} n_F(p)(1 - n_F(l))$ ($\gamma_p^2 - \gamma_{p+\pi/2}^2$)/ $(\gamma_p - \gamma_l)$ changes sign twice as a function of x . This form of the correction to Heisenberg dispersion is comparable to that found in numerical studies of the DE model on a ring [9].

We find that for intermediate densities $0.31(7) < x < 0.92(7)$ in 2D, and $0.31(7) < x < 0.94(2)$ in 3D, $I(x) < 0$ and quantum effects cause a relative softening of spinwave modes near the zone center. This means that the first instability of the DEFM with competing AF exchange interactions is against a spiral phase with $Q^* \approx (0, 0, 0)$. On the other hand, for a small density of electrons (or holes), $I(x) > 0$, and quantum effects instead lead to a relative softening of modes near the zone boundary. In this case the spin-wave spectrum first becomes unstable against a canted spin configuration with $Q^* = (\pi, \pi, \pi)$. These results are in perfect agreement with earlier studies [11]. Finally, we note that if we formally extend our large S analysis to arbitrarily small S , there exists a critical value of spin $S = S^* \approx 1$ (in 3D) for which the DEFM becomes unstable *even in the absence of AF interactions*. This opens up the possibility that for small S (e. g. , $S = 1/2$), the ground state of the DE model may not be a FM, as suggested by some numerical studies [10].

We now proceed to finite T . In a Heisenberg model, finite temperature effects do not change the form of spin-wave dispersion, but the overall scale of the dispersion is reduced by a factor $\propto T^{5/2}/S^2$ [16]. In the case of the DEFM, the result is more complex and coincides with the behavior of a Heisenberg FM only in a very limited range of frequencies and temperatures. Indeed, there are three typical momenta in our problem — an external q , a fermionic p_F , and a typical bosonic momentum $l_{typ} \sim (T/J_1S)^{1/2}$ (in units where the lattice constant $a = 1$). Consider for definiteness the case of small x when $p_F = (6\pi^2x)^{1/3} \ll 1$. Evaluating the self-energy (9) by expanding all γ_k factors to second power in momenta, we obtain in 3D, for $q \ll p_F, (T/J_1S)^{1/2}$

$$\Sigma_T^{(2)}(q) = -\frac{tq^2p_F}{144\pi^2S^2} \frac{1}{N} \sum_l n_B(l) l^2 \Phi\left(\frac{l}{2p_F}\right) \quad (10)$$

where $\Phi(\nu)$ is a smooth function with $\Phi(\nu \rightarrow 0) = 1$, $\Phi(\nu = 1) = 0$, $\Phi(\nu \gg 1) \approx -1/\nu^2$, and

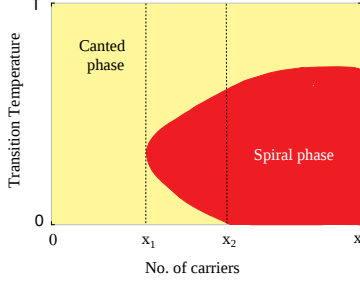


FIG. 3. Phase diagram showing first instability as a function of carrier concentration x and temperature T . For some range of dopings $x_1 < x < x_2$ a re-entrant phase transition is predicted.

$(1/N) \sum_l n_B(l) l^2 \approx (3\zeta(5/2)/16\pi^{3/2}) (T/J_1 S)^{5/2}$. We see that $\Sigma_T^{(2)}(q)$ agrees with the Heisenberg model only at $(T/J_1 S)^{1/2} \leq p_F$. In the opposite limit, we have $\Sigma_T^{(2)}(q) \propto q^2 p_F^3 (T/J_1 S)^{3/2}$. Moreover, the sign of $\Sigma_T^{(2)}(q)$ changes between the two limits.

For large external q : $q \gg p_F$, $(T/J_1 S)^{1/2}$, we obtain

$$\Sigma_T^{(2)}(q) = \frac{t p_F^3}{24\pi^2 S^2 N} \sum_l n_B(l) l^2 \left[1 + \gamma_q - \frac{1}{3} \frac{1 - \gamma_{2q}}{1 - \gamma_q} \right] \quad (11)$$

We see that at these q , the temperature correction to the spin-wave energy is positive, and is of order $p_F^3 (T/J_1 S)^{5/2}$. It depends only weakly on q at intermediate momenta, and vanishes at $q = (\pi, \pi, \pi)$. This result is indeed very different from that in the Heisenberg FM. The temperature correction to the spin-wave dispersion is shown schematically in Fig.2a. A very similar behavior holds in 2D case, the only difference is that the 2D analog of the scaling function $\Phi(\nu)$ does not change sign at $\nu \sim \mathcal{O}(1)$ but rather behaves as $1/\nu^4$ at large ν .

The different nature of quantum/thermal effects in the DEFM and the Heisenberg FM is a result of the different nature of the coupling between spins. In a Heisenberg FM, the $q^2 T^{5/2}$ form of the temperature correction comes from the fact that four-boson vertex scales as $q^2 l^2$ [16]. In the DEFM, the interaction between spin waves is mediated by the charge susceptibility of the Fermi gas, $\Pi(q - l)$ (see Fig. (1e)). At $q, l_{typ} \ll p_F$, $\Pi(q - l)$ can be approximated by $\Pi(0)$, and the effective interaction has the same form as in the Heisenberg FM. However, when $|q - l| \gg p_F$, the susceptibility decreases as $\Pi(m) \propto p_F^2/m^2$. This replaces either one power of $T/J_1 S$ or q^2 factor by p_F^2 in the renormalization of the dispersion, exactly as we found.

The unusual temperature dependence of $\Sigma_T^{(2)}(q)$ gives rise to the possibility of a re-entrant transition between spiral and canted states with varying T . As discussed above, at small p_F , quantum fluctuations favor canted phase. On the other hand, classical fluctuations at low

$(T/J_1 S)^{1/2} < p_F$ soften the dispersion near $q = 0$ and hence favor the spiral state. As a result, the transition line between the two states bends towards smaller x at finite T . However, as T increases and becomes larger than $J_1 S p_F^2$, the sign of $\Sigma_T^{(2)}(q)$ changes, and thermal fluctuations now favor the canted phase. As a result, the transition line now bends towards higher x with increasing T . This can give rise to a re-entrant transition — when T increases at a given, small x , the canted state first becomes unstable towards the spiral state, and then returns back at even larger T . A possible phase diagram for $x \ll 1$ is shown schematically in Fig.2b. The region occupied by the canted phase first shrinks and then expands with increasing T . Qualitatively similar behavior will hold for $1 - x \ll 1$.

To summarize, in this paper we introduce a novel large S expansion scheme for systems with strong Hund's rule coupling, and use it to show how and why the spin dynamics of a DEFM differ from those of a Heisenberg FM. We find that the two models are equivalent at the classical level ($S \rightarrow \infty$), but that both quantum and thermal corrections in the DEFM are different because the interaction between spinwaves is mediated by fermions. We also find that the DEFM provides a new example of an "order from disorder" phenomenon — in the case of a competition between ferromagnetic double exchange and a direct antiferromagnetic superexchange, the classical ground state is infinitely degenerate, but fluctuations lift the degeneracy and select a true intermediate spin configuration, either a canted state or a spiral state, depending on the electron density. This together with the calculated temperature corrections gives rise to the possibility of an unusual re-entrant transition between spiral and canted states with varying T .

The softening of zone boundary spin-waves which we predict *has* been observed in neutron scattering experiments on the CMR Manganites [17], but at a *hole* doping $\tilde{x} = 1 - x \sim 0.3$ for which our zero temperature theory would predict a relative hardening of the dispersion at (π, π, π) . It has been suggested that this softening may be due to the influence of optical phonons [18], or orbital degrees of freedom [19]. We note, however, that the DE mechanism *does* predict a softening at the physically relevant doping, for high enough temperatures. A careful experimental examination of the temperature dependence of the spin-wave spectrum is therefore necessary to determine which mechanism contains the relevant physics.

The issue left for further studies is a possible phase separation in the non-ferromagnetic regime [20]. To study this possibility in our approach, one has to analyze the sign of the longitudinal susceptibility in, e.g., canted phase. If it is negative, then the system is unstable towards phase separation [21]. These calculations are currently under way.

It is our pleasure to acknowledge helpful conversa-

tions with J. Betouras, D. Golosov, R. Joynt and M. Rzechowski. This work was supported under NSF grant DMR-9632527.

-
- [1] C. Zener, *Phys. Rev.* **82**, 403 (1951).
 - [2] P. W. Anderson and H. Hasegawa *Phys. Rev.* **100**, 675 (1955).
 - [3] P. Majumdar and P. Littlewood, *Phys. Rev. Lett.* **81**, 1314 (1998).
 - [4] P.-G. de Gennes, *Phys. Rev.* **118**, 141 (1960).
 - [5] K. Kubo and N. Ohata, *J. Phys. Soc. Jpn.* **33**, 21 (1972).
 - [6] N. Furukawa, *J. Phys. Soc. Jpn.* **63**, 3214 (1994).
 - [7] N. B. Perkins and N. M. Plakida, *Theor. Math. Phys.* **120**, 1182 (1999).
 - [8] A. J. Millis, P. B. Littlewood and B. I. Schraimann *Phys. Rev. Lett.* **74**, 5144 (1995).
 - [9] T. A. Kaplan and S. D. Mahanti, *J. Phys. Condens. Matt.* **9** (1997) and in *Physics of Manganites*, eds. T. A. Kaplan and S. D. Mahanti, Kluwer Academic/Plenum Publishers, New York, 1999.
 - [10] J. Zang et al, *J. Phys. Cond. Matter*, **9**, L157 (1997) and references therein.
 - [11] P. Wurth and E. Muller-Hartmann, *Europhys. J. B* **5**, 403 (1998).
 - [12] D. Golosov, *Phys. Rev. Lett.* **84**, 3974 (2000); *J. Appl. Phys.*, vol. 87, 5804 (2000).
 - [13] A. B. Harris, C. Kallin and A. J. Berlinsky, *Phys. Rev. B* **45**, 2899 (1992); S. Sachdev, *Phys. Rev. B* **45**, 12377 (1992); A. V. Chubukov, *Phys. Rev. Lett.* **69**, 832 (1992).
 - [14] Nic Shannon and A. V. Chubukov, in preparation.
 - [15] Nic Shannon, in preparation.
FM,
 - [16] see e.g., A. I. Akhiezer *et al* "Spin waves", Wiley, NY (1968).
 - [17] H. Y. Hwang *et. al.* , *Phys. Rev. Lett.* **80**, 1316 (1998), Tapan Chatterji, private communication.
 - [18] N. Furukawa, cond-mat/9905123.
 - [19] G. Khaliullin and R. Kilian, *Phys. Rev. B* **61**, 3494 (2000).
 - [20] A. Moreo, S. Yunoki and E. Dagotto, *Science* **283**, 2034 (1999).
 - [21] B.I. Shraiman and E. Siggia, *Phys. Rev. B* **46**, 8305 (1992); A. Chubukov and K. Musaelian, *Phys. Rev. B*
.....